

UDIMET® alloy 188 (UNS R30188) is a cobalt-base alloy with excellent high-temperature strength and good oxidation resistance to 2000°F (1093°C). The high chromium level coupled with small additions of lanthanum produce an extremely tenacious and protective scale. The alloy also has good sulfidation resistance and excellent metallurgical stability as displayed by its good ductility after prolonged exposure to elevated temperatures. Good fabricability and weldability combine to make the alloy useful in gas turbine applications such as combustors, flame holders, liners and transition ducts.

Mechanical Properties

Table 3 - Typical Room Temperature Mechanical Properties of annealed UDIMET alloy 188 Sheet

Yield Strength		Tensile Strength		Elongation
ksi	MPa	ksi	MPa	%
65	446	140	963	55

Table 4 - Rupture Strength of UDIMET alloy 188 Sheet (1000-hr)

Temperature	Rupture Strength	
	ksi	MPa
1300°F / 704°C	35	240
1400°F / 760°C	24	165
1500°F / 816°C	16	110
1600°F / 871°C	10	69
1700°F / 927°C	5.9	41
1800°F / 982°C	3.6	25
1900°F / 1038°C	2.2	15
2000°F / 1093°C	1.3	9

Table 1 - Limiting Chemical Composition, wt %

Carbon.....	0.05-0.15
Manganese.....	1.25 max.
Silicon.....	0.20-0.50
Chromium.....	20.0-24.0
Nickel.....	20.0-24.0
Tungsten.....	13.0-16.0
Lanthanum.....	0.02-0.12
Boron.....	0.015 max.
Iron.....	3.0 max.
Cobalt.....	Balance*

*Reference to the 'balance' of a composition does not guarantee this is exclusively of the element mentioned but that it predominates and others are present only in minimal quantities.


Physical Constants and Thermal Properties

Table 2 - Physical Constants

Density, lb/in ³	0.330
g/cm ³	9.14
Melting Range, °F.....	2375-2425
°C.....	1300-1330
Specific Heat at 70°F, Btu/lb°F.....	0.097
at 21 °C, J/kg°C.....	405
Permeability at 200 oersteds.....	1.0007
Coefficient of Expansion, 0 - 200°F, 10 ⁻⁶ in/in•°F.....	6.6
21 - 93°C, µm/m•°C.....	11.9
Thermal Conductivity, Btu•in/ft ² •h•°F.....	84
W/m•°C.....	12.1
Electrical Resistivity, ohm•circ mil/ft.....	613
microhm-cm.....	102.0



Mechanical Properties (continued)

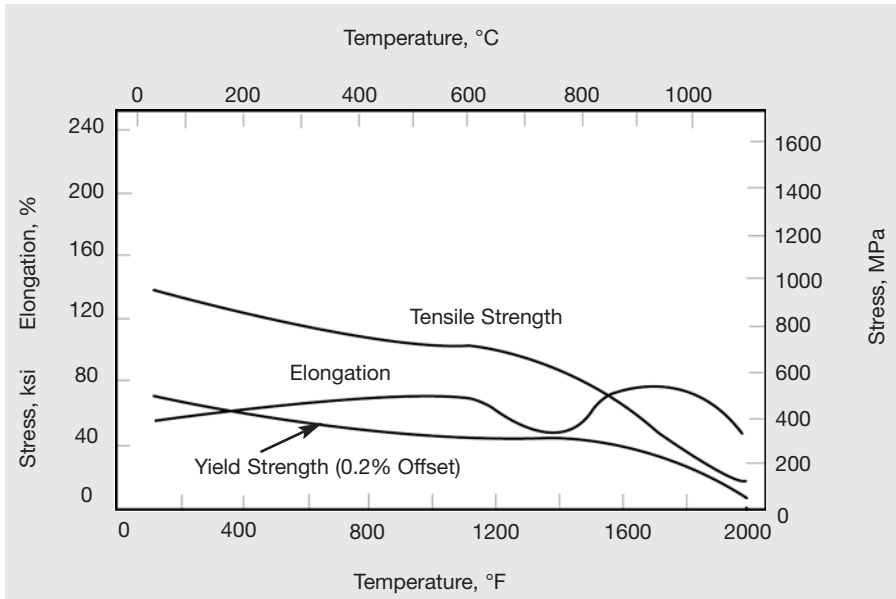

UDIMET alloy 188 retains excellent strength and ductility even at elevated temperatures. The ductility dip at 1400°F (760°C) is due to precipitation of carbides around this temperature.

Figure 1 - Tensile strength, elongation and yield strength of UDIMET alloy 188.

UDIMET alloy 188 work hardens rapidly after cold working due to the abundant carbides. Material can be worked to great extents though and the alloy is not particularly notch sensitive. The hardness also quickly increases in response to cold work and will plateau in the lower 50 Rc range.

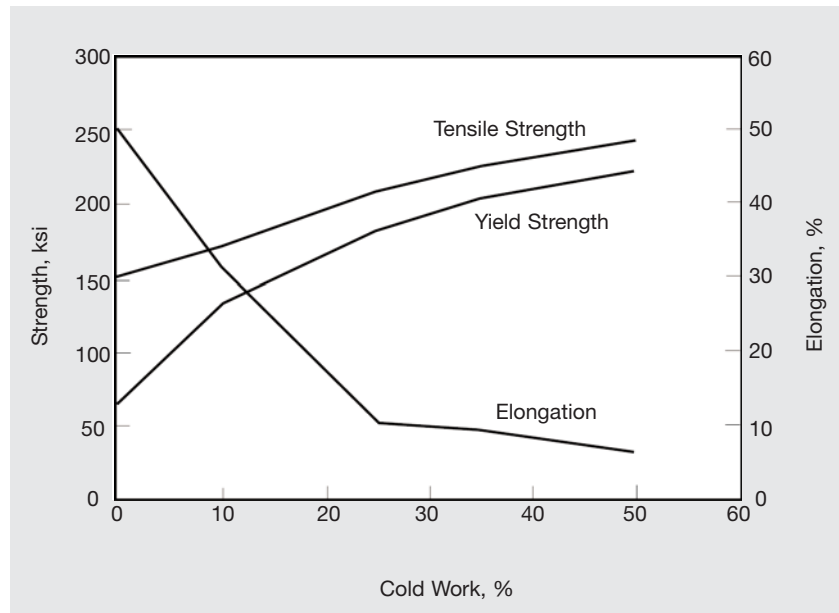


Figure 2 - Effect of cold work on mechanical properties of UDIMET alloy 188.

Microstructure

UDIMET alloy 188 has a stabilized face-centered cubic matrix. Chromium (22%), lanthanum (0.05%) and silicon (0.4%) promote oxidation resistance. Solid solution strengthening is provided by tungsten (14%). Strengthening (see heat treatment details) is further enhanced by the precipitation of M_6C and $M_{23}C_6$ type carbides.

Fabricating

UDIMET alloy 188 has good fabricability. Forming, machining and welding can be carried out by standard methods.

Cold Forming

It is preferable to cold-work the alloy for bending, deep drawing and spinning of components. This is facilitated by the excellent ductility of the alloy, however, high forces may be required to achieve such processing, due to the inherent strength of the alloy. It may therefore be necessary to interstage anneal the material after each step of processing due to the high work hardening rate of the alloy.

Joining

UDIMET alloy 188 can be welded by both manual and automatic welding methods, including shielded metal-arc, gas tungsten-arc (TIG) and gas metal-arc (MIG).

Heat Treatment

UDIMET alloy 188 is normally annealed at 1177°C (2150°F) and rapid air-cooled or water-quenched.

The material can be further strengthened by cold deformation, with enhancement of strength achieved by aging at 540°C (1000°F) for 4 to 16 hours. Note that cold working prior to aging significantly increases the rate at which age hardening can be achieved.

Applicable Specifications

UDIMET alloy 188 is designated as UNS R30188. Contact Special Metals for information on available product forms.

Flat products: AMS 5608

Bar: AMS 5772

Publication Number SMC-065

Copyright © Special Metals Corporation, 2005 (Jan 05)

UDIMET is a trademark of the Special Metals Corporation group of companies.

The data contained in this publication is for informational purposes only and may be revised at any time without prior notice. The data is believed to be accurate and reliable, but Special Metals makes no representation or warranty of any kind (express or implied) and assumes no liability with respect to the accuracy or completeness of the information contained herein. Although the data is believed to be representative of the product, the actual characteristics or performance of the product may vary from what is shown in this publication. Nothing contained in this publication should be construed as guaranteeing the product for a particular use or application.



www.specialmetals.com

U.S.A. Special Metals Corporation

Billet, rod & bar, flat & tubular products

3200 Riverside Drive
Huntington, WV 25705-1771
Phone +1 (304) 526-5100
+1 (800) 334-4626
Fax +1 (304) 526-5643

Billet & bar products

4317 Middle Settlement Road
New Hartford, NY 13413-5392
Phone +1 (315) 798-2900
+1 (800) 334-8351
Fax +1 (315) 798-2016

Atomized powder products

100 Industry Lane
Princeton, KY 42445
Phone +1 (270) 365-9551
Fax +1 (270) 365-5910

Shape Memory Alloys

4317 Middle Settlement Road
New Hartford, NY 13413-5392
Phone +1 (315) 798-2939
Fax +1 (315) 798-6860

United Kingdom

Special Metals Wiggin Ltd.

Holmer Road
Hereford HR4 9SL
Phone +44 (0) 1432 382200
Fax +44 (0) 1432 264030

Special Metals Wire Products

Holmer Road
Hereford HR4 9SL
Phone +44 (0) 1432 382556
Fax +44 (0) 1432 352984

China

Special Metals Pacific Pte. Ltd.

Room 1802, Plaza 66
1266 West Nanjing Road
Shanghai 200040
Phone +86 21 3229 0011
Fax +86 21 6288 1811

Special Metals Pacific Pte. Ltd.

Room 910, Ke Lun Mansion
12A Guanghua Road
Chaoyang District
Beijing 100020
Phone +86 10 6581 8396
Fax +86 10 6581 8381

France

Special Metals Services SA

17 Rue des Frères Lumière
69680 Chassieu (Lyon)
Phone +33 (0) 4 72 47 46 46
Fax +33 (0) 4 72 47 46 59

Germany

Special Metals Deutschland Ltd.

Postfach 20 04 09
40102 Düsseldorf
Phone +49 (0) 211 38 63 40
Fax +49 (0) 211 37 98 64

Hong Kong

Special Metals Pacific Pte. Ltd.

Unit A, 17th Floor, On Hing Bldg
1 On Hing Terrace
Central, Hong Kong
Phone +852 2439 9336
Fax +852 2530 4511

India

Special Metals Services Ltd.

No. 60, First Main Road, First Block
Vasanth Vallabha Nagar
Subramanyapura Post
Bangalore 560 061
Phone +91 (0) 80 2666 9159
Fax +91 (0) 80 2666 8918

Italy

Special Metals Services SpA

Via Assunta 59
20054 Nova Milanese (MI)
Phone +390 362 4941
Fax +390 362 494224

The Netherlands

Special Metals Service BV

Postbus 8681
3009 AR Rotterdam
Phone +31 (0) 10 451 44 55
Fax +31 (0) 10 450 05 39

Singapore

Special Metals Pacific Pte. Ltd.

24 Raffles Place
#27-04 Clifford Centre
Singapore 048621
Phone +65 6532 3823
Fax +65 6532 3621

Affiliated Companies

Special Metals Welding Products

1401 Burriss Road
Newton, NC 28658, U.S.A.
Phone +1 (828) 465-0352
+1 (800) 624-3411
Fax +1 (828) 464-8993

Canada House

Bidavon Industrial Estate
Waterloo Road
Bidford-On-Avon
Warwickshire B50 4JN, U.K.
Phone +44 (0) 1789 491780
Fax +44 (0) 1789 491781

Controlled Products Group

590 Seaman Street, Stoney Creek
Ontario L8E 4H1, Canada
Phone +1 (905) 643-6555
Fax +1 (905) 643-6614

A-1 Wire Tech, Inc.

A Special Metals Company

4550 Kishwaukee Street
Rockford, IL 61109, U.S.A.
Phone +1 (815) 226-0477
+1 (800) 426-6380
Fax +1 (815) 226-0537

Rescal SA

A Special Metals Company

200 Rue de la Couronne des Prés
78681 Epône Cédex, France
Phone +33 (0) 1 30 90 04 00
Fax +33 (0) 1 30 90 02 11

DAIDO-SPECIAL METALS Ltd.

A Joint Venture Company

Daido Shinagawa Building
6-35, Kohnan 1-chome
Minato-ku, Tokyo 108-0057, Japan
Phone +81 (0) 3 5495 7237
Fax +81 (0) 3 5495 1853

