

INCOLOY® alloy MA956 (UNS S67956), first developed as an aerospace superalloy and now used in a range of industrial applications, combines excellent strength and fabricability with outstanding resistance to prolonged exposure up to 1300°C (2400°F). Its exceptional properties result from the mechanical alloying process by which it is made; a process which allows a fine distribution of yttrium oxide particles to be incorporated into a highly corrosion-resistant Fe-Cr-Al alloy.

The alloy has excellent oxidation resistance up to 1300°C (2400°F) and significant creep strength up to its unusually high melting point of 1482°C (2700°F). Thicker sections may be used up to 1370°C (2500°F). Typical industrial applications include hearth rollers, radiant tubes, furnace muffles, fluidized bed retorts, heat treatment baskets, mesh belts, heat shields, burner nozzles, sensor tubes for thermowells and combustion chamber components for diesel engines.

A full range of both hot and cold-worked mill products is available. The forming and machining characteristics are similar to those of conventional high-chromium ferritic steels and Fe-Cr-Al alloys.

**Table 1.** Limiting Chemical Composition, wt.%

Iron .....	Balance*
Chromium .....	18.5-21.5
Aluminum .....	3.75-5.75
Titanium.....	0.2-0.6
Carbon .....	0.1 max.
Yttrium oxide.....	0.3-0.7
Copper.....	0.15 max.
Manganese.....	0.30 max.
Cobalt .....	0.3 max.
Nickel .....	0.50 max.
Phosphorus .....	0.02 max.

\*Reference to the 'balance' of an alloy's composition does not guarantee this is exclusively of the element mentioned, but that it predominates and others are present only in minimal quantities.

## Physical Properties

**Melting point**                      **1480°C (2700°F)**

The unusually high solidus is 100-200°C higher than for most high-temperature nickel-base superalloys. Even at these extremely high temperatures the dispersion of yttrium oxide provides dimensional and structural stability and prevents embrittlement due to grain growth.

**Density**                                **7.25 g/cm<sup>3</sup> (0.262 lb/in<sup>3</sup>)**

The low density is only 70% that of molybdenum allowing INCOLOY alloy MA956 to be economically substituted for similar size fixtures in vacuum furnaces.

The lower mass also reduces loading stresses. Unlike molybdenum, the alloy is completely immune to accidental exposure to air at elevated temperatures.

Publication Number SMC-008  
Copyright © Special Metals Corporation, 2004 (Sept 04)

INCONEL, INCOLOY, and 800HT are trademarks of the Special Metals Corporation group of companies.

The data contained in this publication is for informational purposes only and may be revised at any time without prior notice. The data is believed to be accurate and reliable, but Special Metals makes no representation or warranty of any kind (express or implied) and assumes no liability with respect to the accuracy or completeness of the information contained herein. Although the data is believed to be representative of the product, the actual characteristics or performance of the product may vary from what is shown in this publication. Nothing contained in this publication should be construed as guaranteeing the product for a particular use or application.



Physical Properties, continued

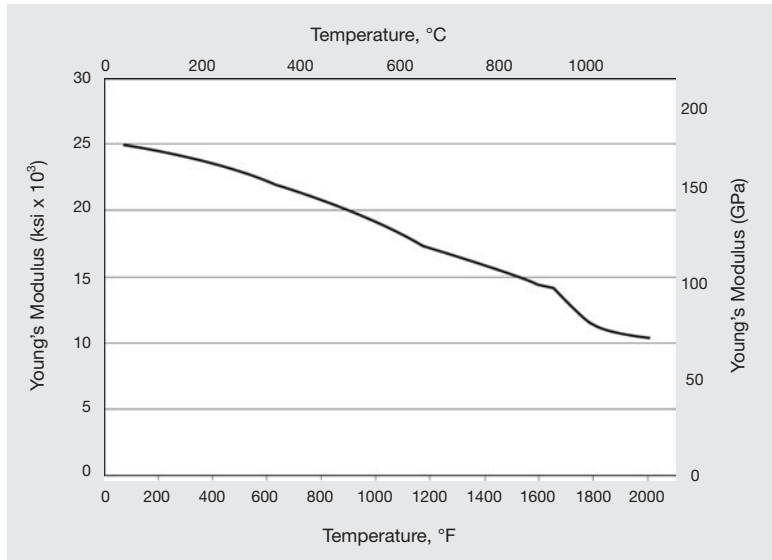


Figure 1. Young's modulus of INCOLOY alloy MA956

Thermal & Electrical Properties

Table 2- Thermal & Electrical Properties

Temp.	Expansion coefficient 10 <sup>-6</sup> •°C	Thermal conductivity W/m•°C	Electrical resistivity μΩ•m	Specific heat J/kg•°C
20	-	10.9	1.31	469
100	11.3	12.2	1.31	491
200	11.6	13.9	1.33	519
300	11.9	15.4	1.34	547
400	12.3	16.9	1.36	575
500	12.7	18.4	1.37	602
600	13.0	19.8	1.39	630
700	13.4	21.2	1.41	658
800	13.9	22.6	1.42	686
900	14.4	24.1	1.43	714
1000	14.9	25.5	1.43	741
1100	15.5	27.0	1.44	769

Thermal Expansion

Compared with nickel-base alloys and austenitic stainless steels, INCOLOY alloy MA956 has the advantage of a relatively low coefficient of thermal expansion.

Resistivity

The material has a high electrical resistance and is suitable for heating applications where the mechanical loading is high.

Thermal Conductivity

This property increases with temperature and is higher than for ceramics. This is of particular advantage in radiant tube and heat-exchanger applications.

## Tensile Properties

### Isotropy

INCOLOY alloy MA956 sheet and plate are rolled in both the longitudinal and transverse directions. After annealing, this results in large pancake shaped grains which minimize directionality in mechanical properties and facilitate the forming of complex shapes from sheet and plate. Tube and bar, mainly processed longitudinally, have a more elongated grain shape and have the highest strength in this direction.

### Retention Of Strength

At the very highest temperatures, the alloy retains significant strength up to the melting point.

At temperatures above 1000°C (1830°F), the alloy is stronger than all conventional, wrought, nickel-base cold-rolled sheet superalloys.

### Ductility

Like many ferritic steels in widespread use, INCOLOY alloy MA956 displays a different response to severe deformation below the Ductile-Brittle Transition Temperature (DBTT). The exact point depends on the product form but is generally in the range 0-100°C (32-212°F).

It is recommended that the usual practice is followed for such steels and pre-warming to 150-200°C (300-400°F) is carried out before forming the material. It may be necessary to warm any tools if chilling of the workpiece is likely.

Maximum ductility occurs at around 650°C (1200°F) and at this temperature the alloy may be readily formed to complex shapes. At temperatures up to 1300°C (2370°F) there is useful ductility which compares very favorably with alternative ceramic materials.

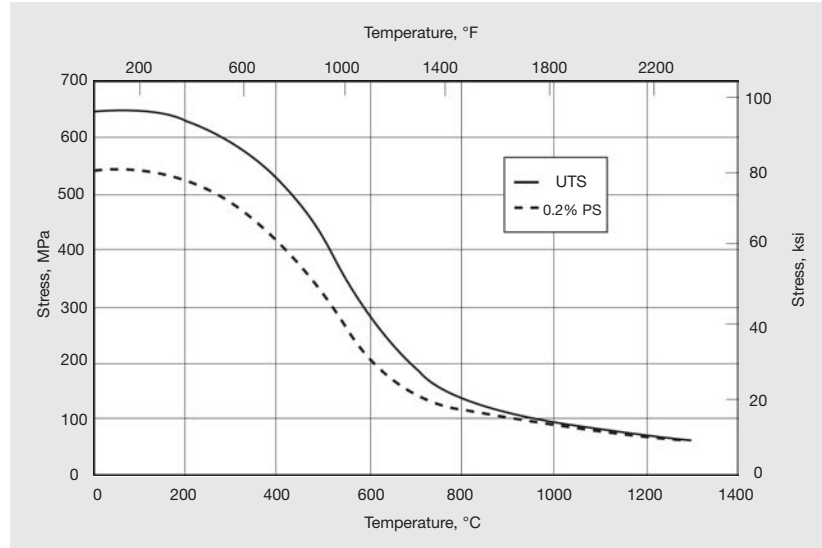


Figure 2. Tensile strength of cold-rolled sheet

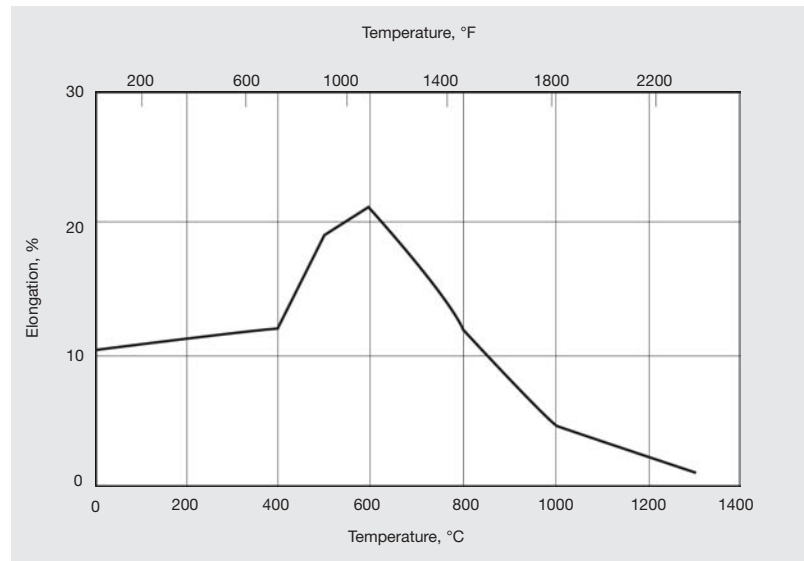


Figure 3. Tensile elongation of cold-rolled sheet

## Creep Properties

INCOLOY alloy MA956 sheet is made by mechanical alloying. Unlike conventional melted alloys, this permits oxide dispersion strengthening (ODS) with microscopic particles of yttrium oxide. This is effective up to the alloy melting point. In addition to ODS, special processing and heat treatment results in a stable, coarse grain size which further enhances the alloy's high-temperature strength.

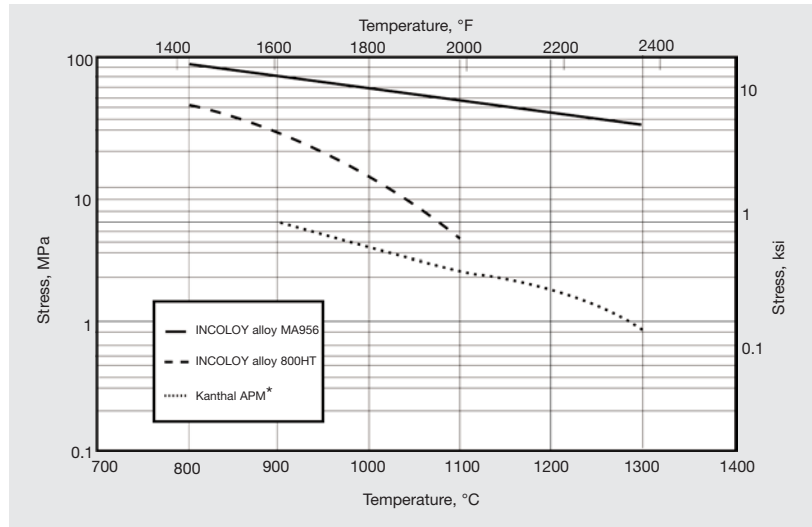


Figure 4. Comparison of 1000-hour creep-rupture strength

A unique feature of ODS alloys is their extreme long-term stability and resistance to creep. The reduction in strength is minimal over very long times compared with conventional Ni-Cr and Fe-Cr-Al alloys, the creep strength advantage above 1000°C (1830°F) being approximately 10-20 times. Using ODS alloys at moderate stresses, it is often possible to disregard the effects of creep.

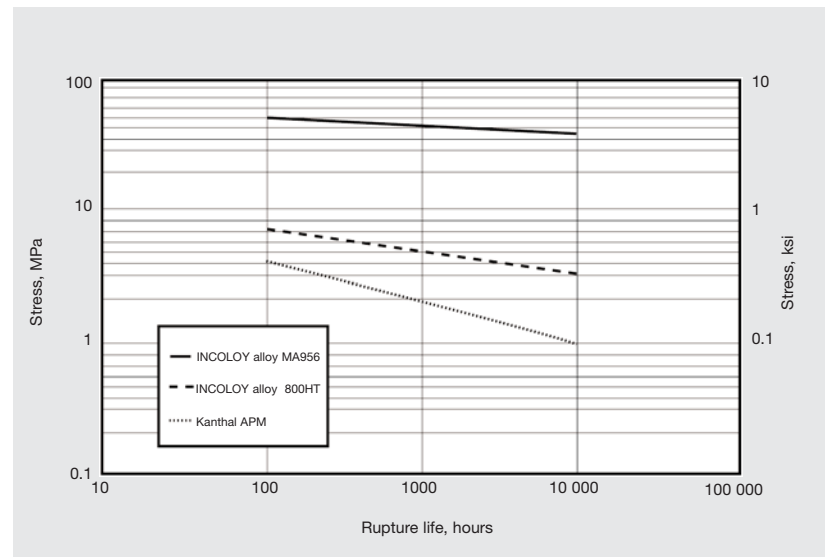


Figure 5. Comparison of creep-rupture life at 1100°C (2012°F)

\*APM is a trademark of Kanthal AB

## Corrosion Resistance

### Oxidation

The high aluminum content of INCOLOY alloy MA956 allows the formation of a thin, highly adherent and protective surface layer of alumina. This process occurs in a wide range of atmospheres, even when levels of oxygen are low. The layer is very effective in reducing the rates of further oxidation. Should the protective layer be mechanically damaged, the high aluminum content of the alloy allows the formation of fresh alumina which heals the affected area. INCOLOY alloy MA956 may be used under oxidizing conditions up to 1300°C (2370°F), much higher than conventional nickel-chromium alloys.

For optimum environmental resistance of machined or cut surfaces, particularly in reducing atmospheres, it is recommended that all traces of lubricants and other foreign matter are removed prior to pre-oxidizing for service in air for 2 hours at 1100°C (2012°F).

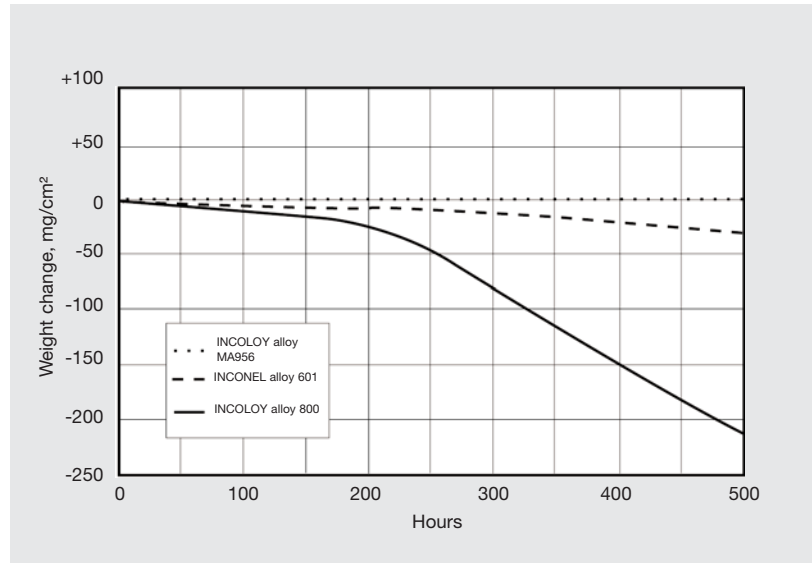


Figure 6. Oxidation resistance at 1205°C (2200°F)

### Carburization

The alumina layer is also a barrier to carburization and sulfidation. Carbon diffusion rates into the base metal are greatly reduced, as is the adherence of carbon deposits on the oxide surface. The relatively clean surface under carburizing conditions also maintains excellent heat transfer rates in radiant heating and chemical processing applications, thus reducing the risk of damage to the alloy through overheating.

### Sulfidation

The adherent aluminum oxide scale formed by the alloy provides a surface barrier to sulfur.

The complete absence of nickel in the alloy avoids the formation of harmful nickel sulfide.

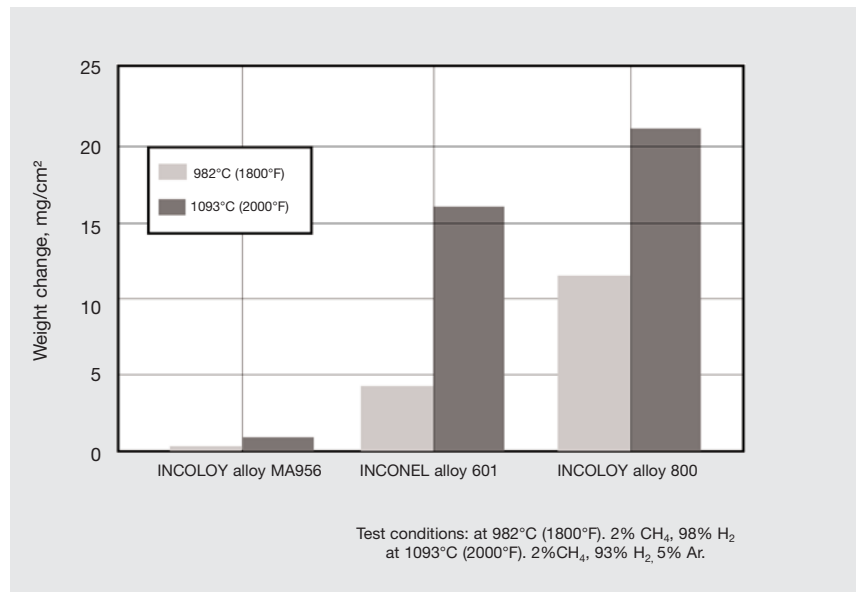


Figure 7. Comparison of carburization resistance

## Working

### Machining

INCOLOY alloy MA956 is readily machined by all conventional techniques. Its hardness is in the range HV 250-300 (Rc 25-30) and the work hardening rate is relatively low compared with nickel-base alloys. The general machining characteristics are similar to type 410 ferritic stainless steel. Although it is possible to use high-speed steel tools it is usually more economical to employ carbide-tipped tools.

Cutting with an abrasive saw requires care to avoid thermal shock which can cause cracking; if possible cooling fluid should be used. If electric discharge machining (EDM) is to be used, the recast surface layer must be subsequently removed by grinding.

### Joining

Conventional TIG welding is possible but produces relatively low strength joints. This process is acceptable for positioning and fillet type welds. Suitable filler wires are INCONEL filler metal 82 for dissimilar metal joints to nickel-base alloys and matching composition wires for welding to austenitic stainless steels. For joining the alloy to itself a Fe-Cr-Al wire is recommended where high-temperature oxidation resistance is required in the weld. The strongest joints are produced by processes with high energy density such as laser and electron beam welding.

If it is impossible to avoid highly restrained joint designs, post-weld stress relieving should be carried out as soon as practicable to avoid delayed stress cracking. A treatment of 2 hours at 1100°C (2010°F) in air followed by air cooling is suggested. The same cycle may serve as a pre-oxidation treatment provided the surface is cleaned of lubricants and other contaminants.

Brazing, diffusion bonding and transient liquid phase bonding (TLP) are possible if extreme care is first taken to remove the protective alumina film by grinding.

For maximum strength at high temperatures, mechanical joints such as matching composition rivets, pins and threaded connections are often used.

### Forming

The nature of INCOLOY alloy MA956 (a ferritic alloy) requires care in high strain rate forming operations such as bending, deep drawing, punching and shearing. For severe deformations it is recommended that the material and tooling is warmed to 150-200°C (300-400°F).

## Product Forms

INCOLOY alloy MA 956 is available in the following forms and sizes:

Form	mm	inches
Cold-rolled sheet	0.7-2.0 thick	0.030-0.080
Hot-rolled plate	3-10 thick	0.120-0.400
Tube	10-110 OD	0.400-4.250
Hot-finished round bar	5.5-50 dia.	0.215-2.000
Cold-drawn wire	2.0-8.5 dia.	0.080-0.335
Flat bar from to	4 x 11 25 x 75	0.160 x 1.0450 1.000 x 3.000

The Special Metals Corporation  
trademarks include: \_\_\_\_\_

**BRIGHTRAY®**  
**CORRONEL®**  
**DEPOLARIZED®**  
**DURANICKEL®**  
**FERRY®**  
**INCOBAR®**  
**INCOCLAD®**  
**INCO-CORED®**  
**INCOFLUX®**  
**INCOLOY®**  
**INCONEL®**  
**INCOTEST®**  
**INCOTHERM®**  
**INCO-WELD®**  
**KOTHERM®**  
**MONEL®**

**NILO®**  
**NILOMAG®**  
**NIMONIC®**  
**NIOTHERM®**  
**NI-ROD®**  
**NI-SPAN-C®**  
**RESISTOHM®**  
**UDIMAR®**  
**UDIMET®**  
**601GC®**  
**625LCF®**  
**718SPF™**  
**725NDUR®**  
**800HT®**  
**956HT™**





www.specialmetals.com

### U.S.A. Special Metals Corporation

#### Billet, rod & bar, flat & tubular products

3200 Riverside Drive  
Huntington, WV 25705-1771  
Phone +1 (304) 526-5100  
+1 (800) 334-4626  
Fax +1 (304) 526-5643

#### Billet & bar products

4317 Middle Settlement Road  
New Hartford, NY 13413-5392  
Phone +1 (315) 798-2900  
+1 (800) 334-8351  
Fax +1 (315) 798-2016

#### Atomized powder products

100 Industry Lane  
Princeton, KY 42445  
Phone +1 (270) 365-9551  
Fax +1 (270) 365-5910

#### Shape Memory Alloys

4317 Middle Settlement Road  
New Hartford, NY 13413-5392  
Phone +1 (315) 798-2939  
Fax +1 (315) 798-6860

### United Kingdom

#### Special Metals Wiggin Ltd.

Holmer Road  
Hereford HR4 9SL  
Phone +44 (0) 1432 382200  
Fax +44 (0) 1432 264030

#### Special Metals Wire Products

Holmer Road  
Hereford HR4 9SL  
Phone +44 (0) 1432 382556  
Fax +44 (0) 1432 352984

### China

#### Special Metals Pacific Pte. Ltd.

Room 1802, Plaza 66  
1266 West Nanjing Road  
Shanghai 200040  
Phone +86 21 3229 0011  
Fax +86 21 6288 1811

#### Special Metals Pacific Pte. Ltd.

Room 910, Ke Lun Mansion  
12A Guanghua Road  
Chaoyang District  
Beijing 100020  
Phone +86 10 6581 8396  
Fax +86 10 6581 8381

### France

#### Special Metals Services SA

17 Rue des Frères Lumière  
69680 Chassieu (Lyon)  
Phone +33 (0) 4 72 47 46 46  
Fax +33 (0) 4 72 47 46 59

### Germany

#### Special Metals Deutschland Ltd.

Postfach 20 04 09  
40102 Düsseldorf  
Phone +49 (0) 211 38 63 40  
Fax +49 (0) 211 37 98 64

### Hong Kong

#### Special Metals Pacific Pte. Ltd.

Unit A, 17th Floor, On Hing Bldg  
1 On Hing Terrace  
Central, Hong Kong  
Phone +852 2439 9336  
Fax +852 2530 4511

### India

#### Special Metals Services Ltd.

No. 60, First Main Road, First  
Block  
Vasanth Vallabha Nagar  
Subramanyapura Post  
Bangalore 560 061  
Phone +91 (0) 80 2666 9159  
Fax +91 (0) 80 2666 8918

### Italy

#### Special Metals Services SpA

Via Assunta 59  
20054 Nova Milanese (MI)  
Phone +390 362 4941  
Fax +390 362 494224

### The Netherlands

#### Special Metals Service BV

Postbus 8681  
3009 AR Rotterdam  
Phone +31 (0) 10 451 44 55  
Fax +31 (0) 10 450 05 39

### Singapore

#### Special Metals Pacific Pte. Ltd.

24 Raffles Place  
#27-04 Clifford Centre  
Singapore 048621  
Phone +65 6532 3823  
Fax +65 6532 3621

### Affiliated Companies

#### Special Metals Welding Products

1401 Burriss Road  
Newton, NC 28658, U.S.A.  
Phone +1 (828) 465-0352  
+1 (800) 624-3411  
Fax +1 (828) 464-8993

Canada House  
Bidavon Industrial Estate  
Waterloo Road  
Bidford-On-Avon  
Warwickshire B50 4JN, U.K.  
Phone +44 (0) 1789 491780  
Fax +44 (0) 1789 491781

#### Controlled Products Group

590 Seaman Street, Stoney Creek  
Ontario L8E 4H1, Canada  
Phone +1 (905) 643-6555  
Fax +1 (905) 643-6614

#### A-1 Wire Tech, Inc.

A Special Metals Company  
4550 Kishwaukee Street  
Rockford, IL 61109, U.S.A.  
Phone +1 (815) 226-0477  
+1 (800) 426-6380  
Fax +1 (815) 226-0537

#### Rescal SA

A Special Metals Company  
200 Rue de la Couronne des Prés  
78681 Epône Cédex, France  
Phone +33 (0) 1 30 90 04 00  
Fax +33 (0) 1 30 90 02 11

#### DAIDO-SPECIAL METALS Ltd.

A Joint Venture Company  
Daido Shinagawa Building  
6-35, Kohnan 1-chome  
Minato-ku, Tokyo 108-0057, Japan  
Phone +81 (0) 3 5495 7237  
Fax +81 (0) 3 5495 1853

